


Tested element: **SGG Stadip Protect 64.2**

Sample surface area S = 1,9 m²
Volume of receiving room V = 86 m³
Volume of source room 98 m³

FREQ. Hz	R dB
100	27,8
125	29,0
160	32,5
200	31,8
250	32,8
315	33,0
400	33,2
500	35,6
630	35,1
800	33,4
1000	33,3
1250	36,7
1600	39,8
2000	41,8
2500	44,5
3150	46,9
4000	50,0
5000	51,5

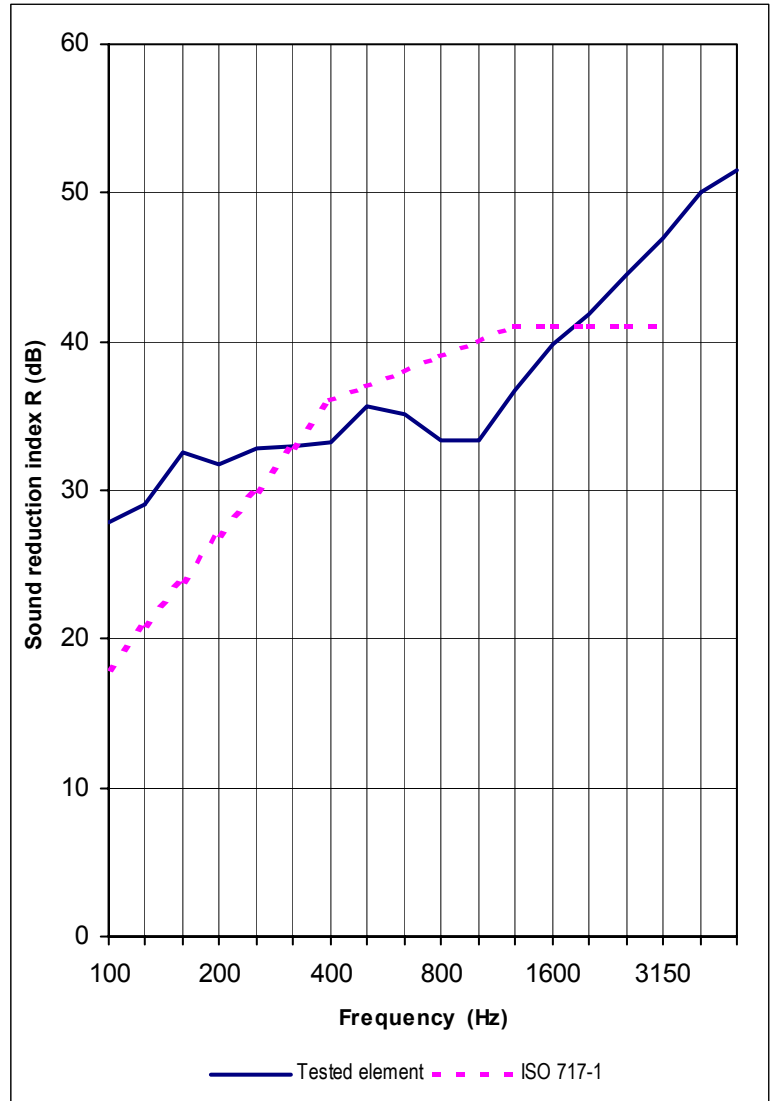

Rating according to ISO 717-1 (in the band 100 ÷ 3150 Hz) based on laboratory measurements:

R_w (C; C_{tr}) = 37 (0 ; -2) dB